


Tested element: **SGG Planilux 4 mm**

Sample surface area S = 1,9 m²
Volume of receiving room V = 86 m³
Volume of source room 98 m³

FREQ. Hz	R dB
100	22,0
125	21,9
160	22,9
200	21,2
250	21,3
315	22,5
400	25,0
500	27,7
630	29,4
800	30,8
1000	32,4
1250	33,6
1600	35,0
2000	34,9
2500	31,2
3150	24,0
4000	28,2
5000	30,7

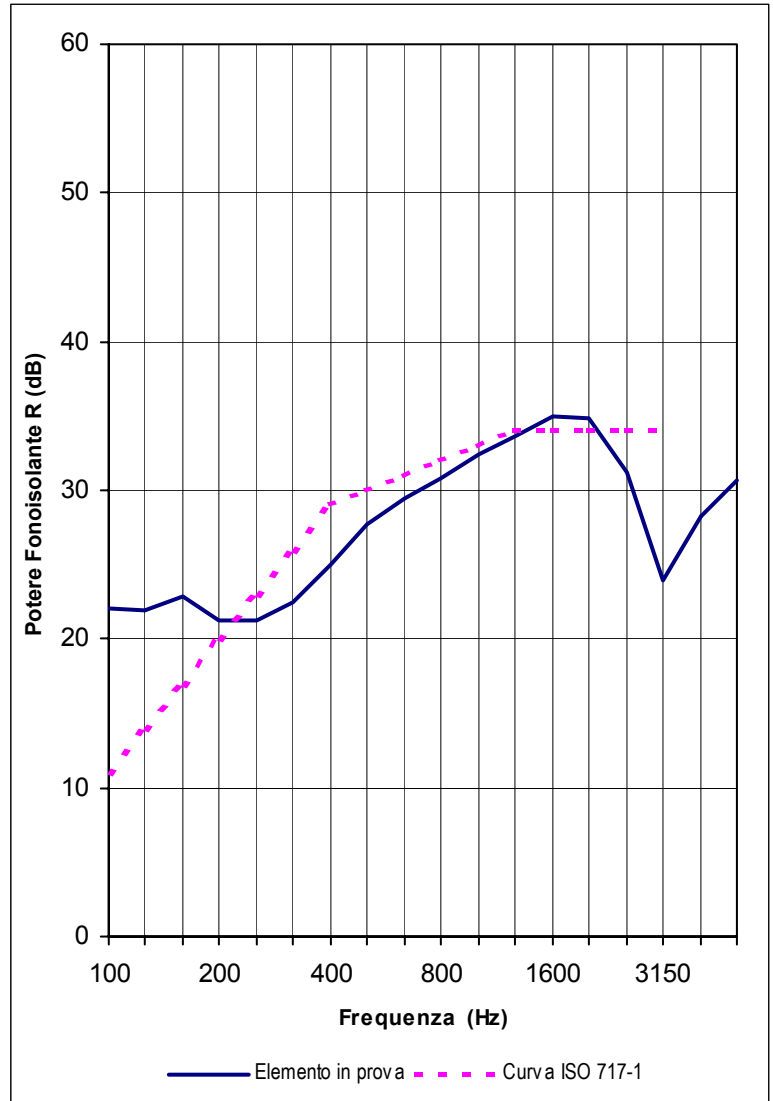

Rating according to ISO 717-1 (in the band 100 ÷ 3150 Hz) based on laboratory measurements:

R_w (C; C_{tr}) = 30 (-2 ; -2) dB