


TEST RESULTS

Tested element: **SGG Planilux 3 mm**

Sample surface area S = 1,9 m²
Volume of receiving room V = 86 m³
Volume of source room 98 m³

FREQ. Hz	R dB
100	18,5
125	18,7
160	21,7
200	18,3
250	19,7
315	20,8
400	22,9
500	26,0
630	27,0
800	28,5
1000	30,1
1250	31,5
1600	33,2
2000	34,0
2500	34,0
3150	32,3
4000	22,9
5000	23,9

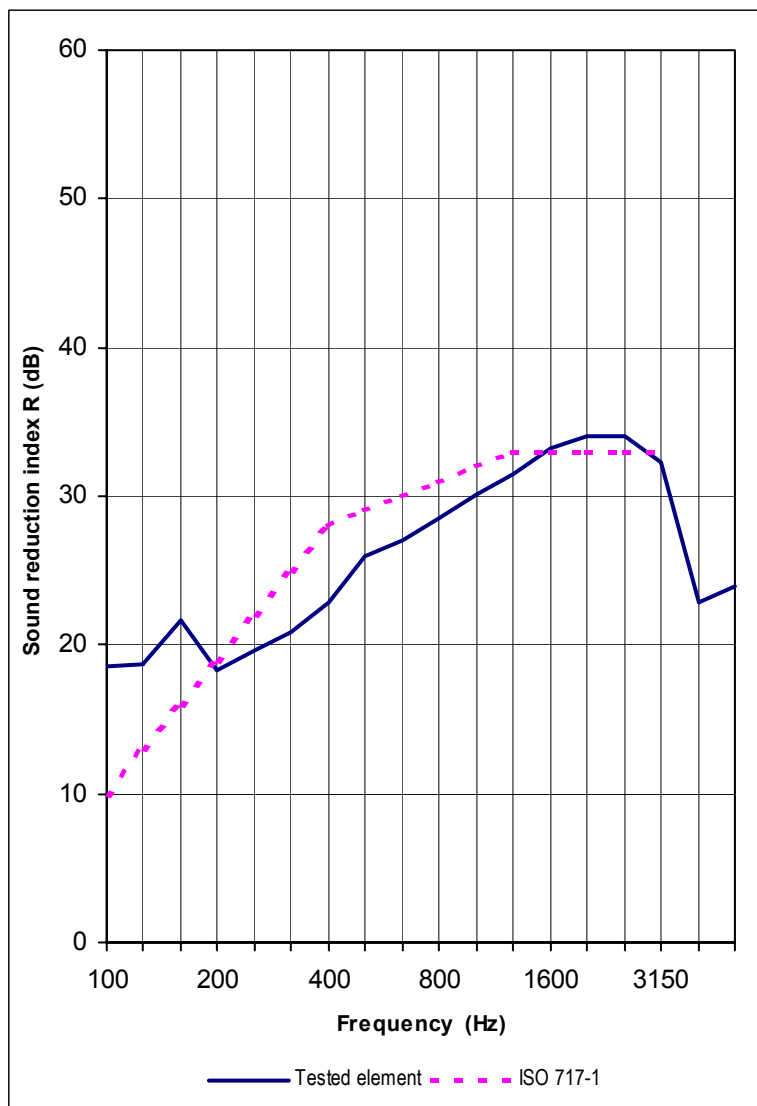

Rating according to ISO 717-1 (in the band 100 ÷ 3150 Hz) based on laboratory measurements:

R_w (C; C_{tr}) = 29 (-1 ; -3) dB